REPORT DOCUMENTATION PAGE

Form Approved OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suppostsions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188).

, ,

1. REPORT DATE (DD-MM-YYYY)	1. REPORT DATE (DD-MM-YYYY) 2. REPORT TYPE		3. DATES COVERED (From - To)
9/12/2012	Performance/Technical Repo	t (Final)	10/1/2011 - 9/12/2012
. TITLE AND SUBTITLE		5a. C0	ONTRACT NUMBER
olyfibroblast: A Self-Healing and	Galvania Protection Additiva		
bry horobrast. A Sen-ricaning and	Carvaine Protection Additive	5b. Gi	RANT NUMBER
		5 05	N00014-09-1-0383
		5c. Pr	ROGRAM ELEMENT NUMBER
. AUTHOR(S)		5d PF	ROJECT NUMBER
enkoski, Jason J.			
CHROSKI, Jason J.		5e. T/	ASK NUMBER
			FGY25
		5f W	ORK UNIT NUMBER
. PERFORMING ORGANIZATION NA	AME(S) AND ADDRESS(ES)		8. PERFORMING ORGANIZATION
he Johns Hopkins University App	lied Physics Laboratory		REPORT NUMBER
1100 Johns Hopkins Rd aurel, MD 20723			
aurer, wid 20725			
SPONSORING/MONITORING AGE	NCY NAME(S) AND ADDRESS(ES)		10. SPONSOR/MONITOR'S ACRONYM(S)
ffice of Naval Research	The state of the s		ONR
75 North Randolph Street			
rlington, VA 22203-1995			11. SPONSOR/MONITOR'S REPORT
			NUMBER(S)
A DIOTOIDUTION INVANABILITY OF	PATPARPAIT		
2. DISTRIBUTION/AVAILABILITY ST approved for Public Release: distr	ibution is Unlimited.		
	~	0 0-	- A
	2012	0927	800
3. SUPPLEMENTARY NOTES			
4. ABSTRACT			
he goal of this project is to develo			ity of skin by forming a polymer scar across
ratches. Designed to work with e			s of microscopic, hollow zinc tubes filled
	e-urea (MCPU), when scratched, the I		
ith a moisture-cured polyurethane		are needed sir	ica tha nalumarization is drivan by ambiant
ith a moisture-cured polyurethand oken tubes and completely fills the	he crack. No catalysts or curing agents	are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethan oken tubes and completely fills the		are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethan oken tubes and completely fills the		are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethand oken tubes and completely fills the		are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethan coken tubes and completely fills the		are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethand token tubes and completely fills the sumidity.		are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethan roken tubes and completely fills the sumidity.	he crack. No catalysts or curing agents	are needed sir	ice the polymerization is driven by ambient
ith a moisture-cured polyurethan token tubes and completely fills the similar transfer.	he crack. No catalysts or curing agents	are needed sir	ce the polymerization is driven by ambient
ith a moisture-cured polyurethand token tubes and completely fills the similarity. 5. SUBJECT TERMS prosion protection, self-healing, or self	ne crack. No catalysts or curing agents		
tith a moisture-cured polyurethand roken tubes and completely fills the sumidity. 5. SUBJECT TERMS perrosion protection, self-healing, of the security classification of:	coatings, polymers	JMBER 19a. N	AME OF RESPONSIBLE PERSON
ith a moisture-cured polyurethan	coatings, polymers 17. LIMITATION OF 18. N ABSTRACT 0	JMBER 19a. NA	

Award Information

Award Number	N00014-09-1-0383	
Title	Polyfibroblast: A Self-Healing & Galvanic Protection Additive	
Principal Investigator	Dr. Jason J. Benkoski	
Organization	The Johns Hopkins University Applied Physics Laboratory	

Technical Section

Objective

Corrosion costs over \$300 billion per year in the US, and as much as \$4 billion per year to the Navy alone. The most cost effective method for preventing rust is to paint the surface. This protection, however, is only temporary, as paint inevitably develops scratches. The ability to make more durable coatings must be balanced against the convenience of spray painting. The latter requirement effectively limits the feasible options to polymeric coatings, which, in turn, constrains the maximum achievable wear resistance. The objective of this program is to achieve revolutionary gains in corrosion protection by developing self-healing, damage tolerant coatings, rather than pursue incremental gains in damage resistance.

Approach

JHU/APL has developed Polyfibroblast, a paint additive for commercial-off-the-shelf (COTS) primers that confers self-healing and galvanic protection capacity to the primer (Figure 1). Polyfibroblast consists of paint-filled microcapsules and zinc powder. It has been shown to prevent rusting for 6 weeks in a salt fog chamber. Standard CARC coatings rust within hours, and zinc-rich CARC coatings rust within one week by comparison (Figure 2). Polyfibloblast delivers dramatic performance gains without requiring retooling, retraining, reformulation, or significant added cost.

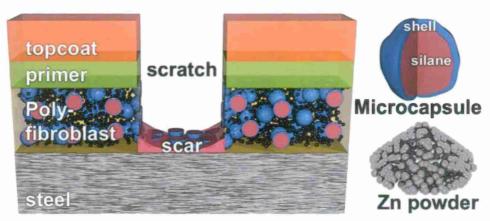


Figure 1. Polyfibroblast contains fresh paint encapsulated in polymer shells plus Zn powder. When scratched, resin from the broken microcapsules fills the crack to form a polymer scar. Zn powder supplies galvanic protection in the event of incomplete healing.

Progress

The corrosion protection of Polyfibroblast self-healing paint was optimized by adjusting three parameters: silane type, silane concentration, and zinc dust loading. Experiments revealed that the three variables are interdependent and must be varied simultaneously to determine the optimum formulation. Figure 2 displays several of the best performing formulations. Note the exceptional performance of Polyfibroblast across a wide range of parameter space. This variety is perhaps most impressive in Figure 3, where over 20 formulations display major performance advantages over the CARC and zinc-rich CARC controls. In general, the combination of zinc powder and microcapsules performed better than either alone. Silanes that formed monolayers (octadecyltrimethoxy silane, OTS) tended to work best at high silane concentration and high zinc loading. Silanes that operated as wetting agents (glycidoxypropyl-trimethoxy silane, GPS) worked best at low silane concentration and low zinc loading.

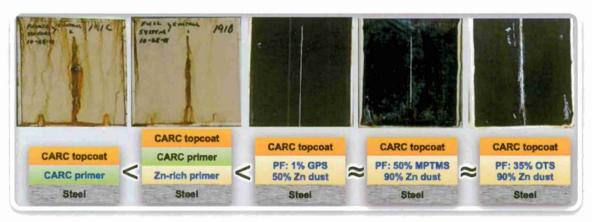


Figure 2. 6 week salt fog panels compared for standard CARC coatings and Polyfibroblast.

Electrochemical Impedance Spectroscopy (EIS) further supported these findings by providing direct evidence of self-healing. Figure 4 shows that the impedance of the original coating was on the order of $100,000~\Omega$, but immediately following the scratch, it would fall to about $100~\Omega$. The self-repair mechanism would then restore the impedance to within an order of magnitude of the original value within 48 hours. Together with the galvanic protection of the zinc dust, corrosion within the scratch is completely arrested.

Based on the salt spray, moisture resistance tests, and electrochemical impedance spectroscopy, there was no clear winner in terms of self-healing and corrosion protection. However, 65% OTS microcapsules with a 90% zinc dust loading provide the best option when additional factors such as cost, shelf life, and environmental risks are taken into account.

OTS works best at low loading: Since it forms a molecular monolayer, a small volume spreads across a large area. The low volume fraction offsets the extra cost of the microcapsules and benefits the mechanical properties of the primer. OTS hydrolysis is slow: Polyfibroblast microcapsules degrade by reacting with water and solidifying prematurely. OTS microcapsules show no loss of performance after one year of storage. OTS has a lower environmental and health risk: OTS formulations are somewhat unique for fact that they work in the absence of any polymer film. Unlike other silanes that must work in tandem with isocyanate precursors, pure OTS will passivate exposed steel. By eliminating toxic components such as monomeric IPDI, OTS microcapsules can be handled in the open with little risk to health or the environment.

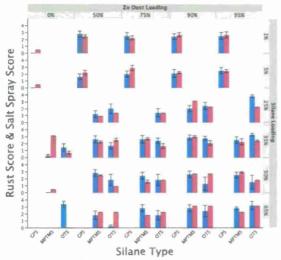


Figure 3. Plot moisture resistance rust score (blue) and salt spray scores (red) for samples prepared in FY12. For comparison, the zincrich control primer averaged a rust score of 2 and a salt spray score of 3. 65% OTS with 90% Zn dust was chosen as the best formula.

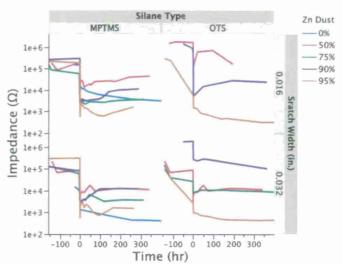


Figure 4. Plot of the magnitude of complex impedance at 0.36 Hz versus time for Polyfibroblast coatings. Impedance spectroscopy directly observes self-healing in real time, and it shows recovery to within an order of magnitude of the original impedance.

Cumulative Statistics

Documentation / Publications

M. W. Patchan, L. M. Baird, Y.-R. Rhim, E. D. LaBarre, A. J. Maisano, and J. J. Benkoski "Liquid-Filled Metal Microcapsules," ACS Applied Materials & Interfaces 4 (2012) 2406-2412.

L. M. Baird, M. W. Patchan, J. L. Breidenich, Y.-R. Rhim, E. D. LaBarre, A. J. Maisano, R. M. Deacon, E. Ott, J. J. Benkoski, "Self-Healing Coatings with Galvanic Protection," *PCI Magazine*, (2012) March Issue.

Conference presentations/proceedings

A. J. Maisano, R. Srinivasan, M. W. Patchan, L. M. Baird, E. D. LaBarre, J. J. Benkoski, "Environmental and Temporal Characterization of a Self-Healing Coating with Galvanic Protection," Pacific Rim Meeting on Electrochemical and Solid-State Science, Honolulu, HI, Oct 7-12, 2012.

Invention disclosures/patents

Nonprovisional Patent Application, "Self-Healing Coatings," August 29, 2012. USPTO patent application number 2011-0293958-A1

Students/Postdocs supported by this award N/A

Other noteworthy recognition

- Received praise and interest from Michael Halloran, Science and Technology Director for the Program Executive Office of Land Systems for the US Marine Corps
- This program will receive development support for transitioning the self-healing paint technology to the US Marine Corps variant of the Joint Light Tactical Vehicle (JLTV)